

Environmental Safety and Health (ESH) Impacts of Emerging Nanoparticles and Byproducts from Semiconductor Manufacturing

Tasks 425.023 and 425.024

Research Team

PIs:

- **Jim A Field, Dept. Chemical and Environmental Engineering, UA**
- **Scott Boitano, Dept. of Physiology & Arizona Respiratory Center, UA**
- **Buddy Ratner, University of Washington Engineered Biomaterials Center, UWEB**
- **Reyes Sierra, Dept. Chemical and Environmental Engineering, UA**
- **Farhang Shadman, Dept. Chemical and Environmental Engineering, UA**

Graduate Students:

- **Isabel Barbero: PhD candidate, Chemical and Environmental Engineering, UA**
- **Christopher Barnes, PhD completed, Chemical Engineering, UW**
- **Rosa Daneshvar: PhD candidate, Chemical Engineering, UW**
- **Cara L Sherwood: PhD candidate, Cell Biology and Anatomy, UA**
- **Hao Wang: PhD candidate, Chemical and Environmental Engineering, UA**

Other Researchers:

- **Antonia Luna, Postdoctoral Fellow, Chemical and Environmental Engineering, UA**
- **Citlali Garcia, Postdoctoral Fellow, Chemical and Environmental Engineering, UA**
- **Angel Cobo, Exchange MS Student, Chemical and Environmental Engineering, UA**
- **Jacky Yao, Research Scientist, Chemical and Environmental Engineering, UA**

Cost Share (other than core ERC funding):

- **\$80k from UA Water Sustainability Program**

Overall Objectives

- **Characterize toxicity of current and emerging nanoparticles (NP) & NP byproducts**
- **Develop new rapid methodologies for assessing and predicting toxicity**

ESH Metrics and Impact

1. *Reduction in the use or replacement of ESH-problematic materials*

This project will evaluate the toxicity of various types of nanoparticles utilized or considered for application in semiconductor manufacturing, and the impact of manufacturing steps on their toxicity. This information can assist in selecting materials which are candidates for replacement or use reduction.

2. *Reduction in emission of ESH-problematic material to environment*

The knowledge gained can be utilized to modify the manufacture of nanoparticles so that they have a lowered toxicity and thus a lowered environmental impact.

Surface Physical Characterization


Hypothesis: The size and size distribution of nanoparticles intrinsically makes them more adsorptive to external chemicals, and these surface molecules lead to the observed toxic effects of nanoparticles on cells.

Surface Physical Characterization



- **Particle size distribution (dynamic light scattering)**
- **Specific area (area/volume or area/mass of NP)**
- **Active site density; site energetics**
- **Physical adsorption vs chemical adsorption**
- **Ability of the surface to concentrate bulk contaminants (selective adsorption)**
- **Retention of contaminants**

Surface Physical Characterization

Objective: determine surface ability to concentrate and retain bulk contaminants. Key parameters are specific area, active site density, and surface energetics for selective adsorption

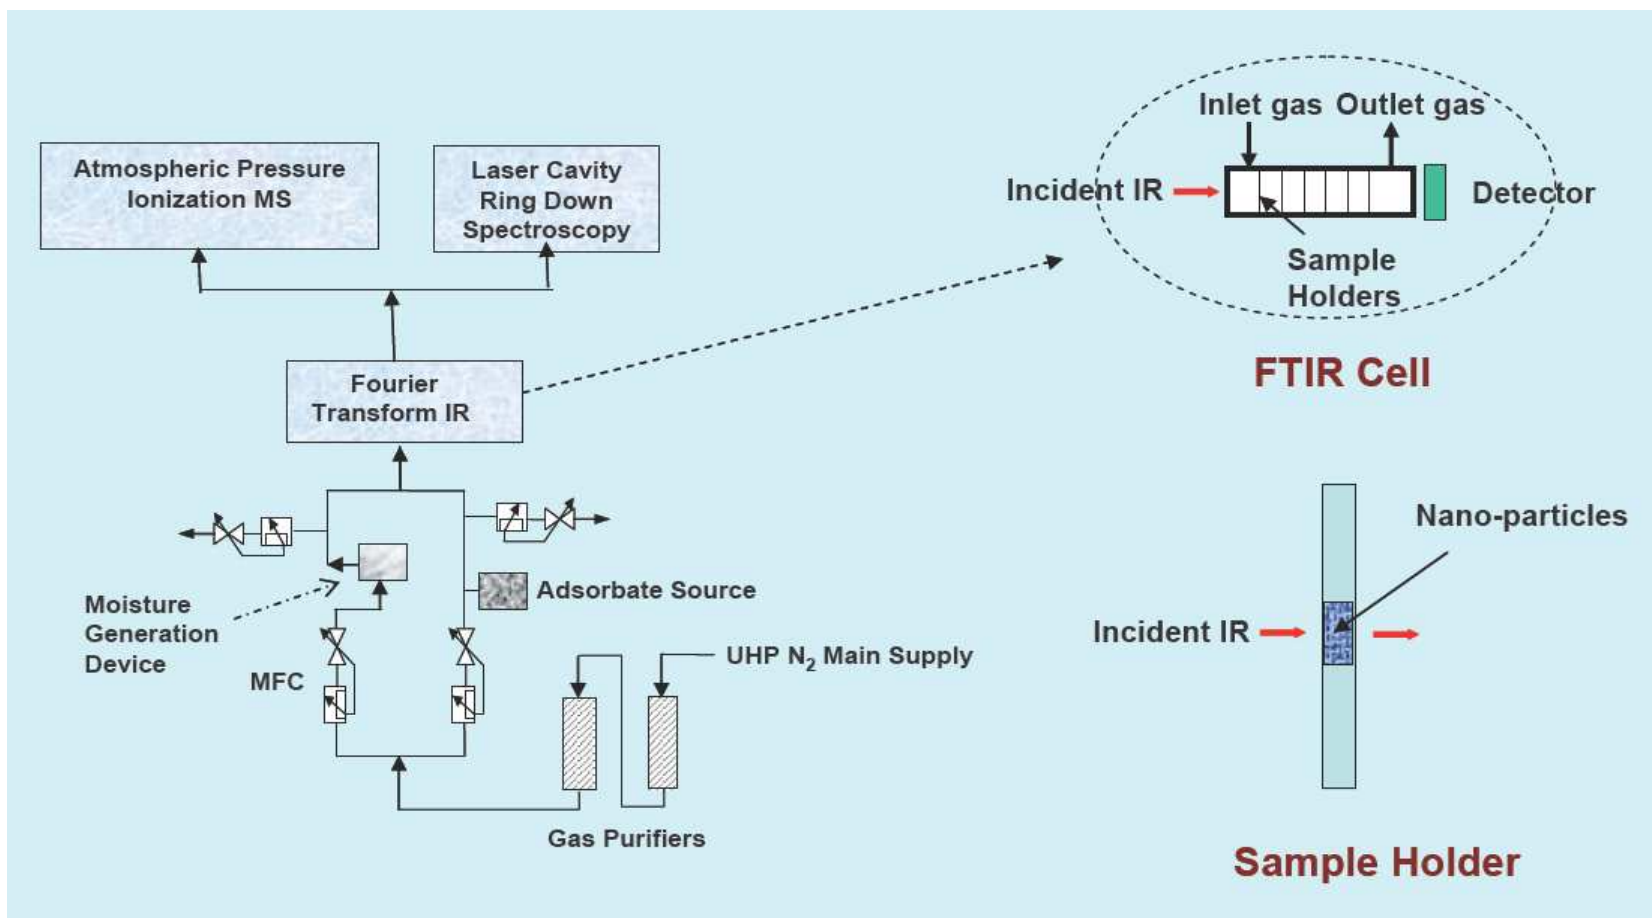


Experimental Method & Typical Results

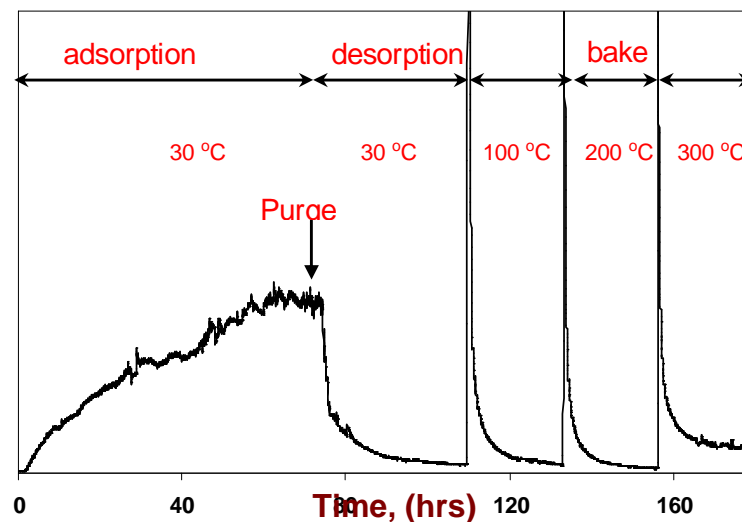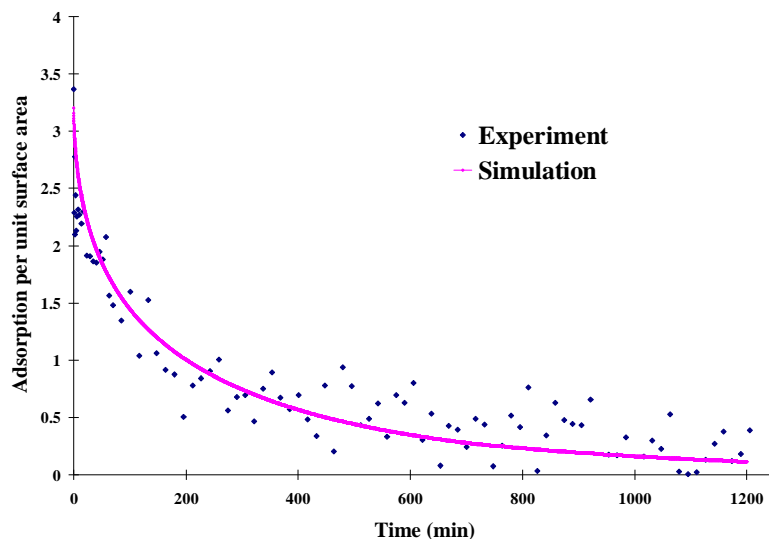

- **Physical adsorption of inert adsorbent (similar to BET isotherm) for area measurement**
- **Chemical adsorption of reactive adsorbent for measuring site density**

- **Temperature-Programmed Interaction (TPI) for measuring site energetics**


Comparison of Surface Activity of Different NP Materials

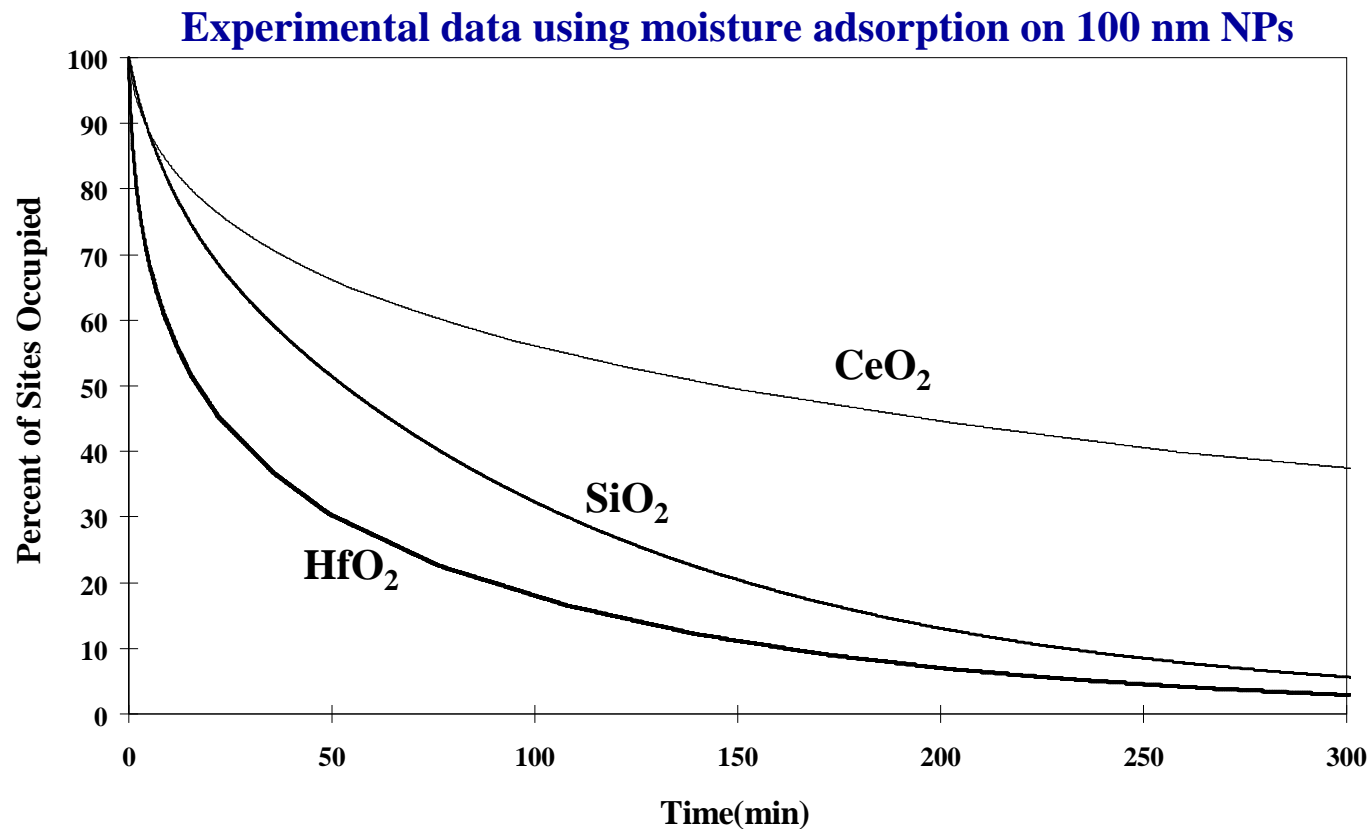

Contamination retention is compound dependent: highest for CeO₂ and lowest for HfO₂; adsorption on CeO₂ seems to be strong chemisorption

NPs Retention of Contaminants

Dynamics of Moisture Desorption

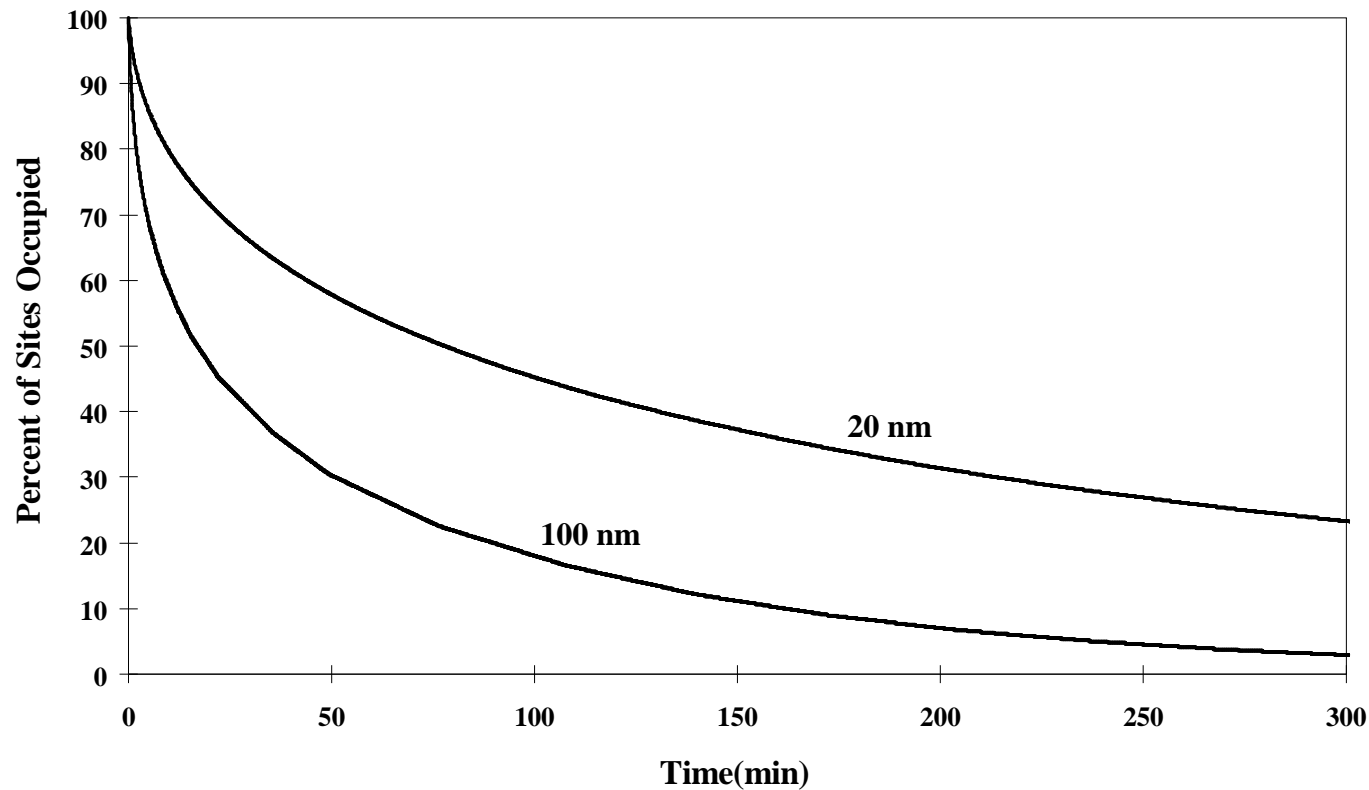

Contamination retention of NPs is size dependent (smaller NPs show higher retention)


Surface Characterization

	Particle Size	Adsorption Rate Coeff.	Desorption Rate Coeff.	Active Site Density	Adsorption Capacity
	d_p (nm)	k_a ($\text{cm}^3 \text{ mol}^{-1} \text{ s}^{-1}$)	k_d (s^{-1})	S_0 (mol/cm^2)	C_{s0} (mol/cm^2)
HfO ₂	20	3.30E+08	2.4	7.00E-10	6.56E-10
HfO ₂	100	8.00E+08	0.8	2.50E-10	2.48E-10
SiO ₂	20	5.30E+08	360	2.00E-08	2.74E-09
CeO ₂	20	3.00E+08	1	8.75E-10	8.49E-10


- Small HfO₂ particles adsorbed contaminants more energetically than larger particles (*higher activation energy*)
- Small particles have higher *capacity* for adsorption and retention of secondary contaminants

Fractionation of CeO₂ by Centrifugation

Fractioning CeO₂ 2g/L Eppendorf Centrifuge 4500 rpm

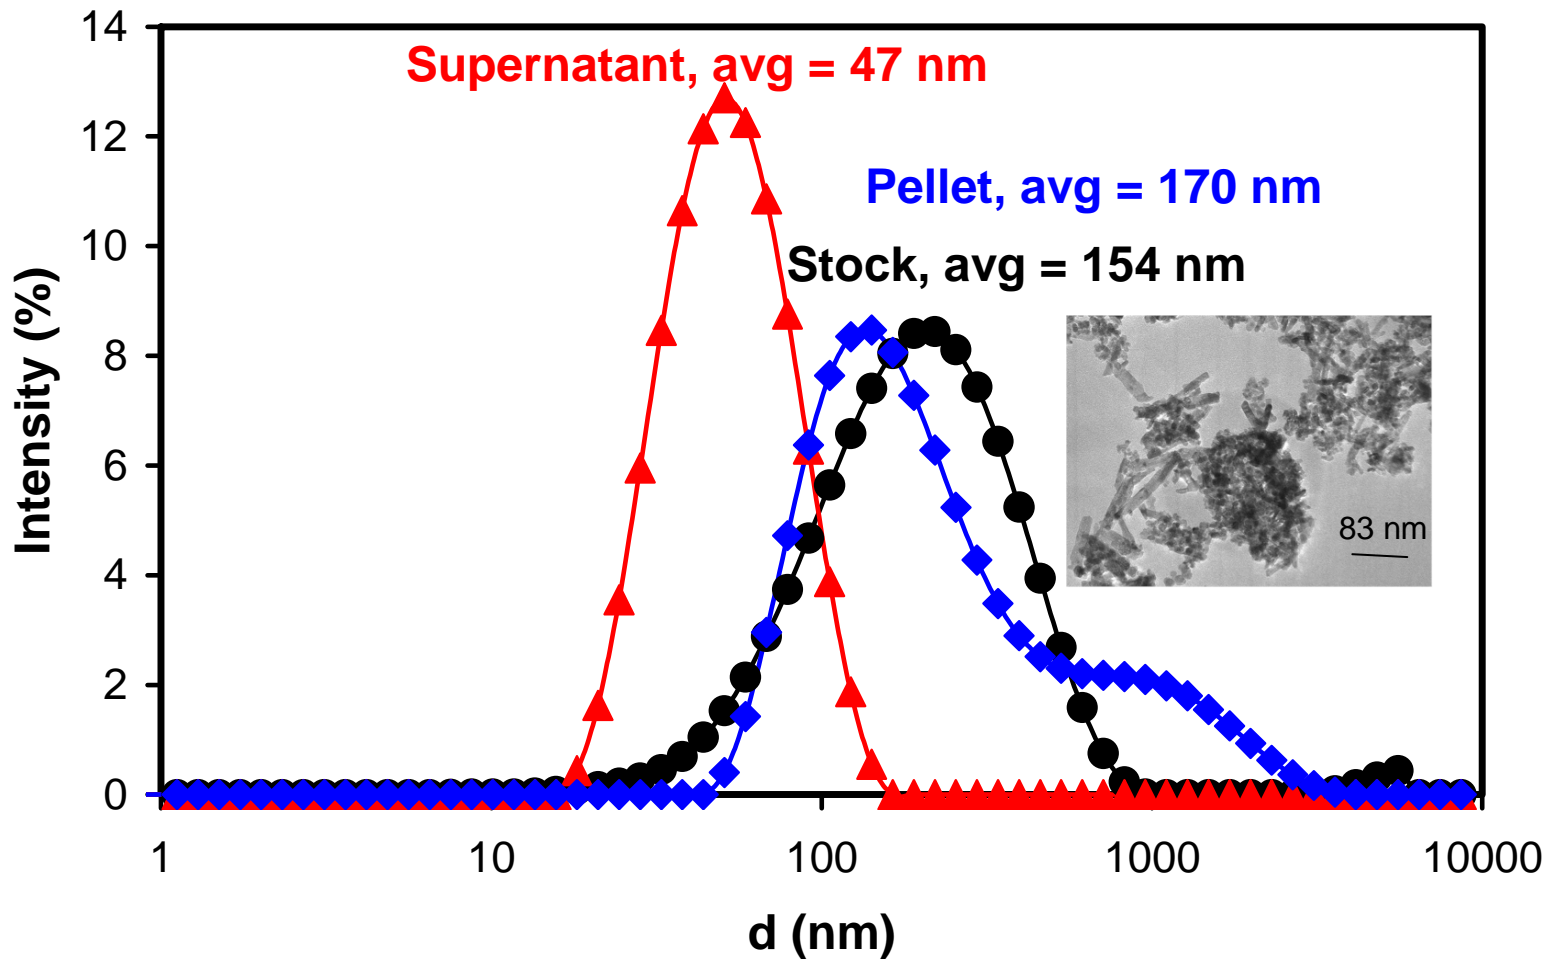

Role Surfactant Conc. on CeO₂ NP Size

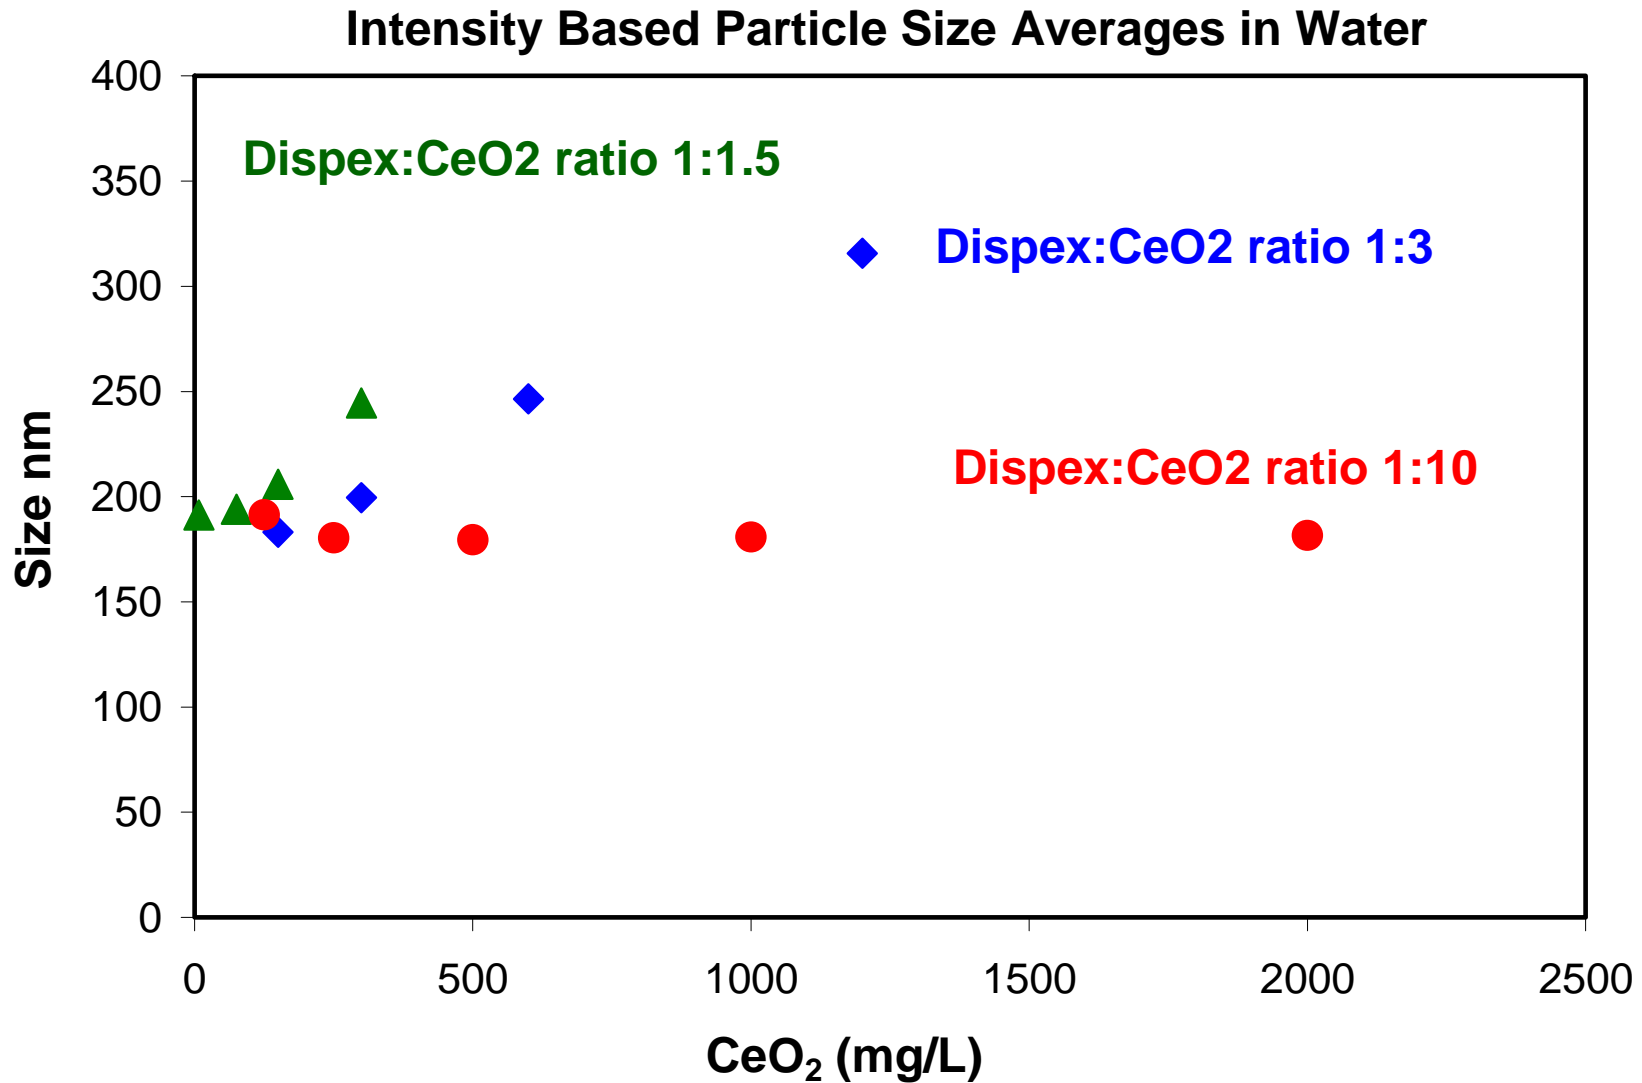

Impact Biological Media on NP Dispersions

Intensity Based Particle Size Averages in Water (DLS)
(units = nm)

<u>MEDIUM</u>	<u>MATERIAL</u>		<u>Comment</u>
	<u>HfO₂</u>	<u>CeO₂</u>	
MQ Water	359 ± 12	1741 ± 275	
MQ Water + dispex	138 ± 2	209 ± 25	
MTT	284 ± 2		MTT = mitochondrion toxicity test medium
HBSS	3242 ± 270		HBSS = Hanks' Balanced Salt Solutions
DMEM	593 ± 252		DMEM = Dulbecco's Modified Eagle Medium (+25KBS, no HCO ₃)
Microtox	901 ± 406	236 ± 21	

Surface Chemical Characterization

The University of Washington has a strong campus resource facility permitting us to perform state-of-the-art nanoparticle surface analysis. Instrumentation that is available for this purpose includes:


- Electron spectroscopy for chemical analysis (ESCA)**
- Secondary ion mass spectrometry (SIMS)**
- Surface plasmon resonance (SPR)**
- Atomic force microscopy (AFM)**
- Sum Frequency Generation (SFG)**
- Attenuated Total Reflectance IR (ATR-IR)**

Secondary Ion Mass Spectrometry (SIMS)


Time-of-flight (ToF) SIMS; Static SIMS



- Probably the most information-rich of the modern surface analysis methods
- Various organic/inorganic contaminants detected on the surface of HfO_2 NPs

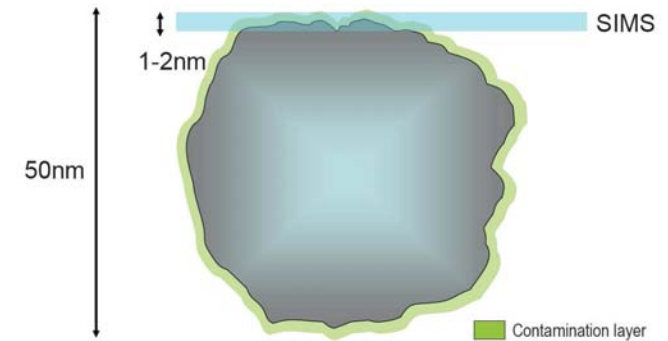

- Positive and negative spectra can be used to identify impurities including metals from fabrication or organics from unidentified sources

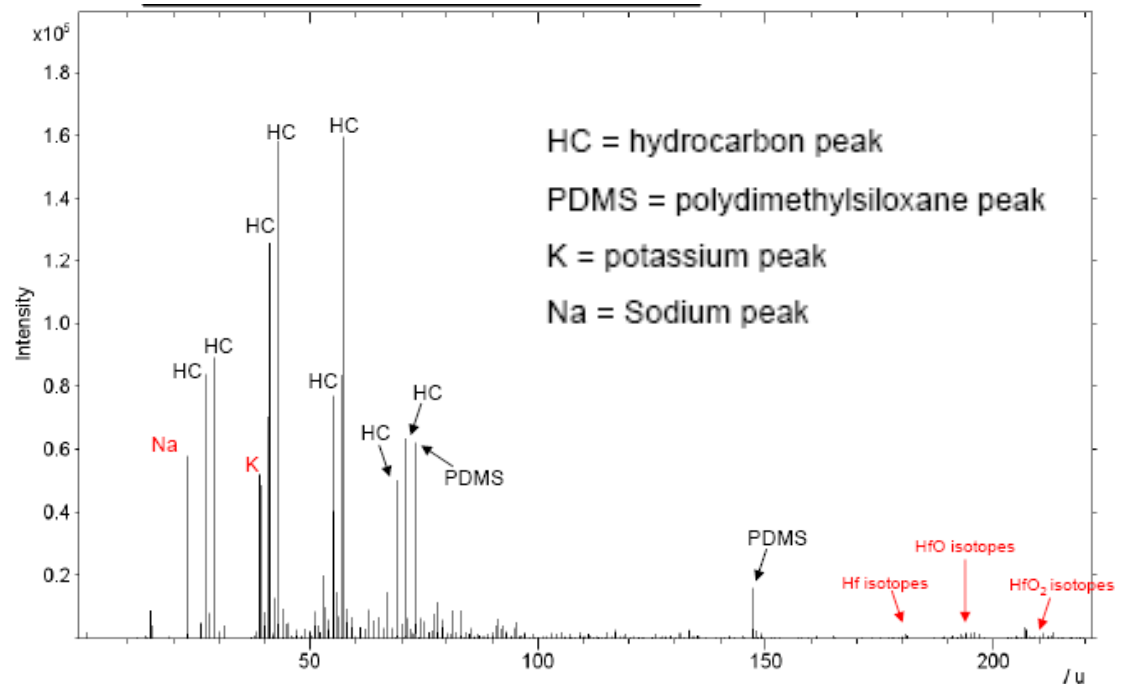

Nanoparticle Impurities – ToF SIMS

Positive Spectra Impurities

mass	ID	Ref Micron	NP1 20 nm	NP2 1-2 nm	NP3 100 nm
27	Al	+	+		+
28	CH ₂ N	+	++		++
30	CH ₄ N	+	+		+
40	Ca	++			+
45	C ₂ H ₅ O	++		++	+
46	C ₂ H ₆ O	+		+	+
52	C ₃ H ₂ N		+		+
55	Fe	+			+
58	Ni		+		
78	C ₂ H ₆ O ₃		+		
90	Zr	++	+		+
118	C ₅ H ₁₂ NO ₂	+		+	+
135	C ₉ H ₁₁ O	++		++	+
161	C ₁₁ H ₁₃ O	++		+++	+

“+” represents presence of listed fragment. “++” and “+++” are used to indicate relative amounts of listed fragments within row and cannot be used to compare rows one to another.

SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing

Nanoparticle Impurities – ToF SIMS

Negative Spectra Impurities

mass	ID	Ref Micron	NP1 20 nm	NP2 1-2 nm	NP3 100 nm
19	F	+++	+	++	++
26	CN	+	++		+
31	P		+		
35	Cl	+++	+	+	++
47	PO	+	++		
51	CIO	+			
59	C ₂ H ₃ O ₂	+		++	
78	C ₃ H ₇ OF		+		
78.96	PO ₃		+		
78.92	⁷⁹ Br	+	++		
81	⁸¹ Br	+	++		
104	C ₃ H ₈ N ₂ O ₂		+		
127	I	+			
205	C ₁₃ H ₁₉ NO			+	

“+” represents presence of listed fragment. “++” and “+++” are used to indicate relative amounts of listed fragments within row and cannot be used to compare rows one to another.

SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing


Surface Characterization

Summary/Preliminary Conclusions

SIMS Analysis

Impurity	Ref Micro	NP1 20 nm	NP2 1-2 nm
Light Organics (<100 MW)	+	+	+
Heavy Organics (>100 MW)			+
Silicon	+		+
Chlorine	+	+	
Bromine		+	
Rare Earth Metals	+	+	+


Catechol Treated CeO₂ XPS Spectra

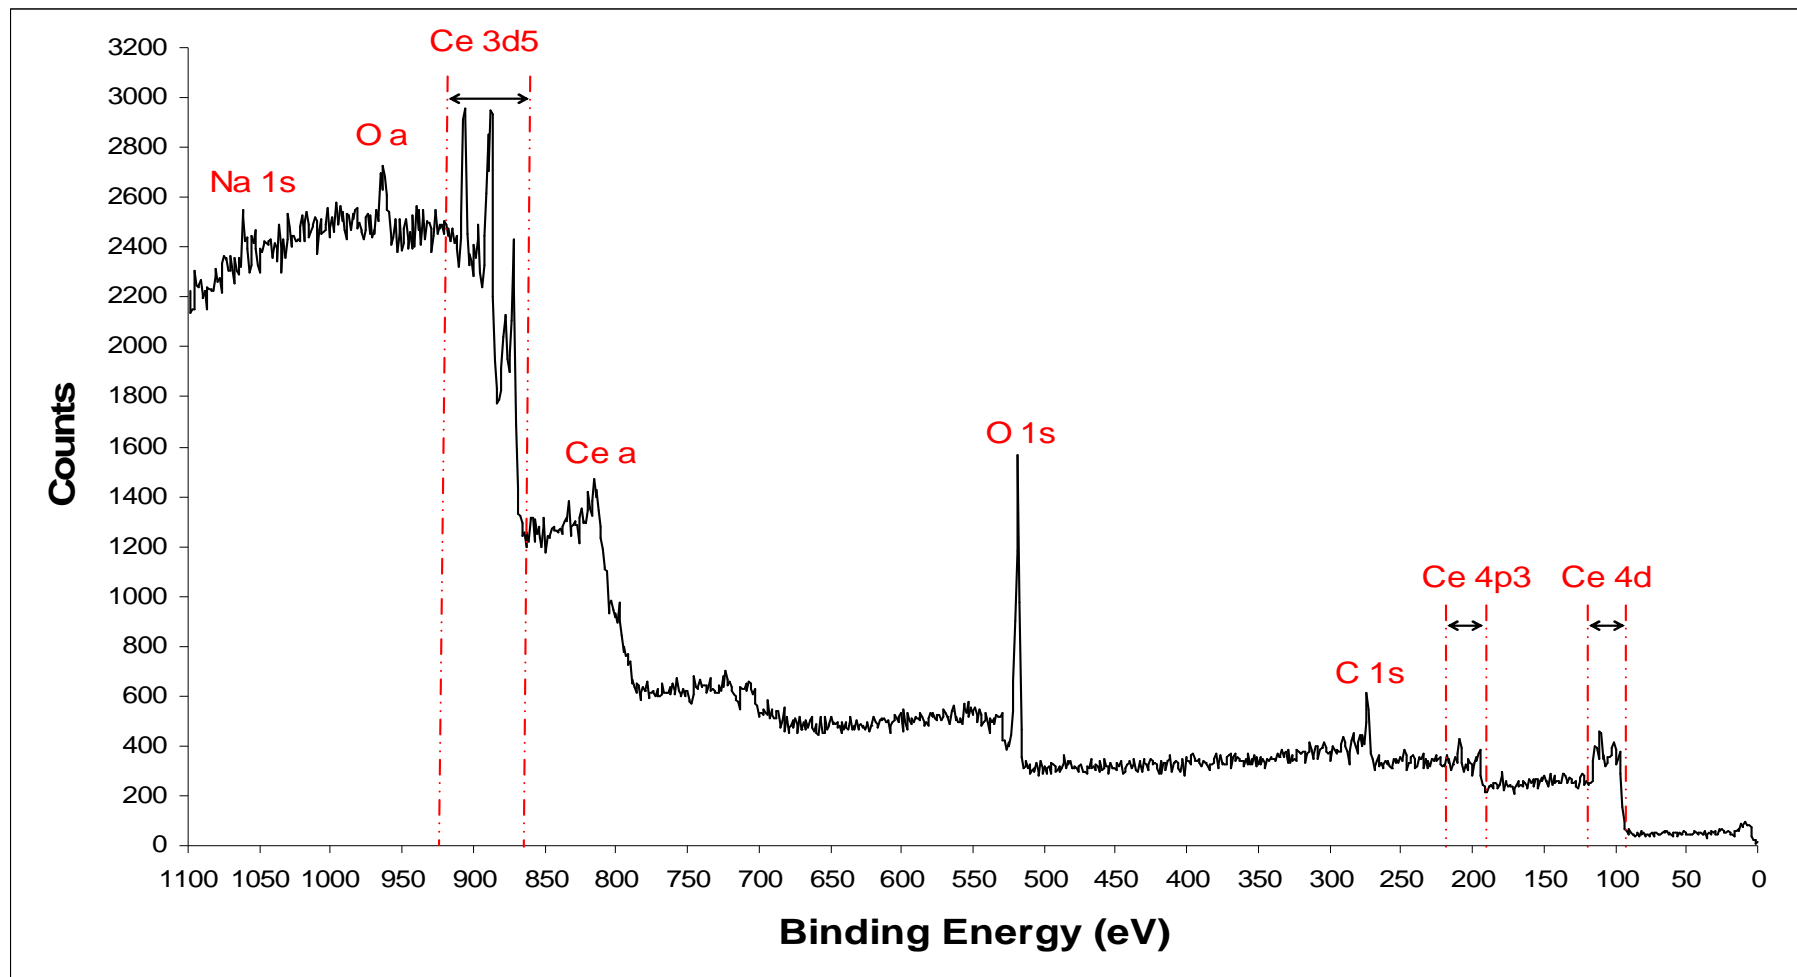


Sodium, carbon, cerium and oxygen were observed in the spectrum

SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing

CeO₂ Core Level XPS Spectra Comparison

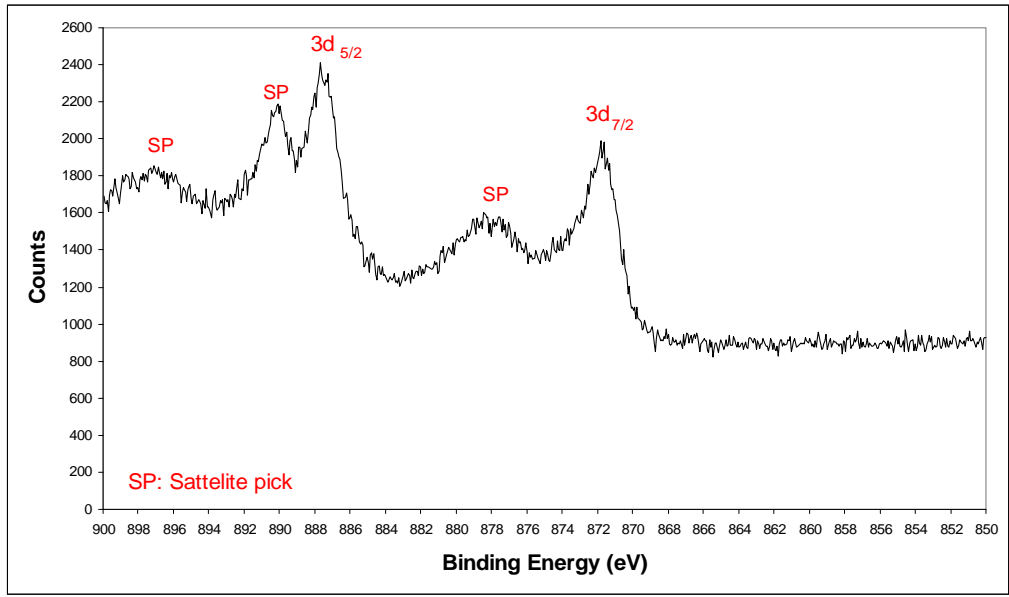

High resolution XPS spectra of catechol treated CeO₂

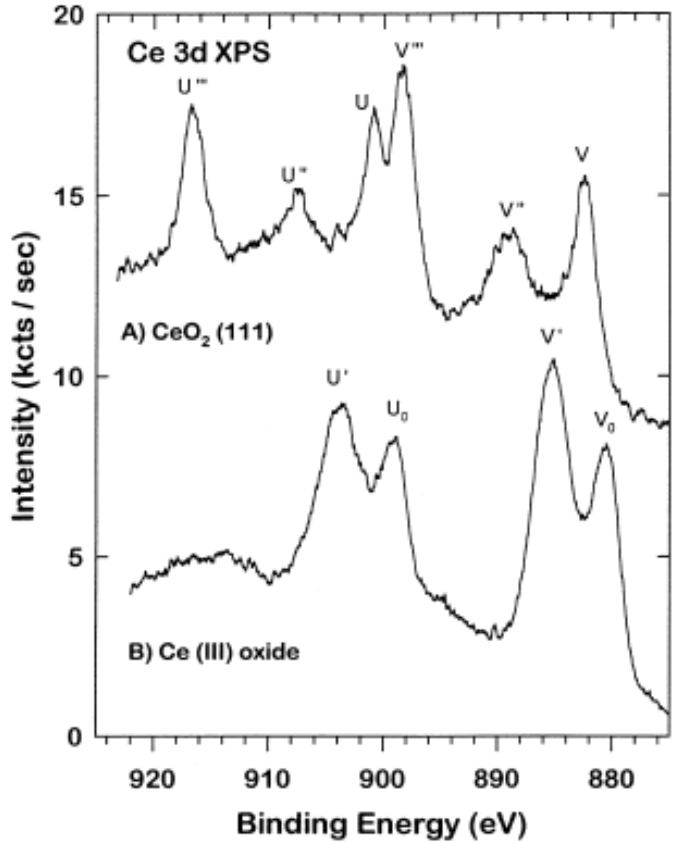

Ce 3d core level photoemission spectra from (A) CeO₂ (111), (B) Ce (III) oxide*

* D.R. Mullins, S.H. Overbury, D. R. Huntley. Surface Science 409 (1998) 307-319.

Surface Chemistry Results and Future Plans

- **Our central hypothesis about the presence of surface contaminant species and high surface adsorptiveness of these nanoparticles is supported by our data.**
- **Comparison between Ce3d photoemission spectra of catechol treated CeO₂ and literature suggests that sample is in Ce⁴⁺ state.**
- **It has been shown in the literature that X-ray emission might have an effect on the oxidative state of the sample.**
- **In order to find the oxidative state of a pristine sample, the effect of x-ray on CeO₂ nanoparticles should be investigated.**

Toxicity Assessment and Prediction

Objectives

- **Establish role for reactive oxygen species (ROS) and oxidative stress as a potential marker for NP toxicity assessment**
- **Develop predictable models of toxicity based on physico-chemical properties elucidated by advanced surface analysis techniques**
- **Validate toxicity assessments and predictions with organ skin cultures (and advanced lung cultures)**

Materials


- Nanoparticles

Hafnium Oxide (HfO_2), immersion lithography

Silica Oxide (SiO_2), CMP

Ceria Oxide (CeO_2), CMP

Others (Al_2O_3 , carbon and germanium- nanotubes, quantum dots *etc*)

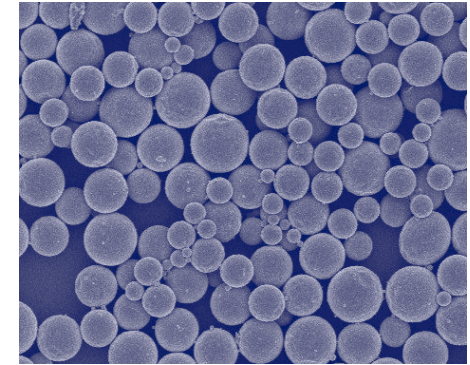

- Biological targets


Human skin cell line (HaCat)

Human lung epithelial cell line (16HBE14o-)

Human foreskin rafted organ culture (ROC)

Bacterium (*Vibrio fischeri*) Microtox test


Others (methanogens, bacterial cultures, yeast *etc*)

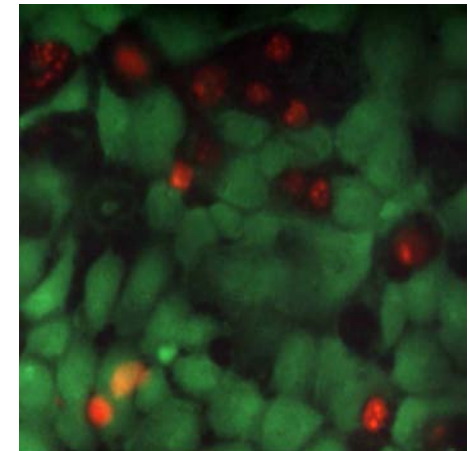

Methods


- Main Toxicity Tests Utilized

Live/Dead Assay with HaCat Skin Cell Line (HaCat)

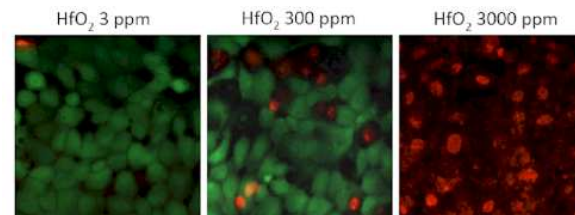


Live: calcein AM) Dead: ethidium homodimer-1

Mitochondrial Toxicity test (MTT) (ureter cells)

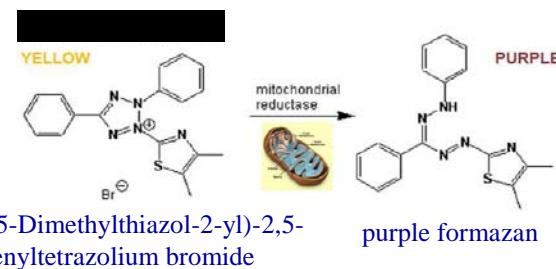


Microtox (*Vibrio fischeri*)

Methanogenic Activity

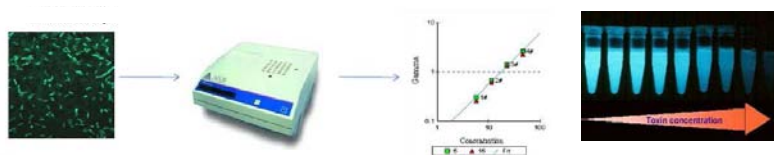

- Chemical: Reactive Oxygen Species (ROS) Production





Detection of fluorescent ROS-sensitive dye

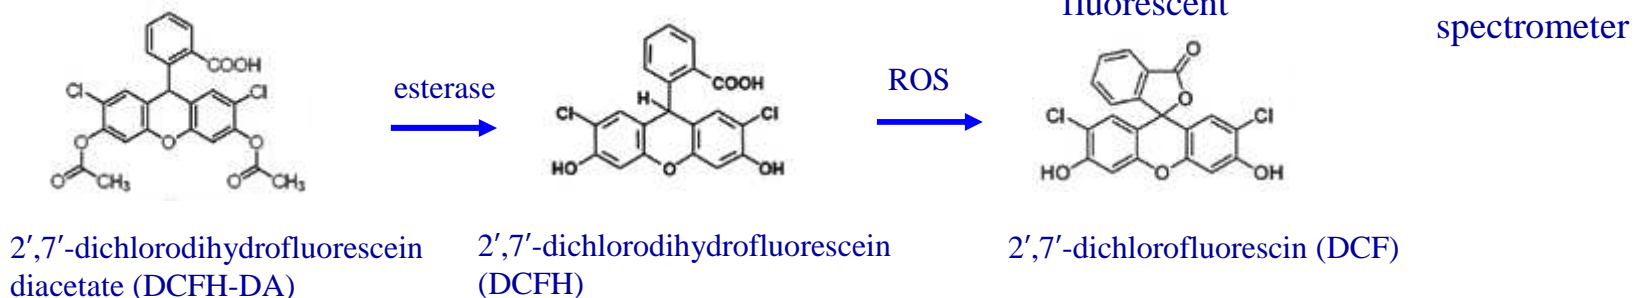

Results on HfO₂

Four distinct batches of hafnium oxide tested. Example Live/Dead test (HaCat skin cells)


Batch	Measured ----- avg size (nm) -----	Manufact. Reported
Batch 1	360	20
Batch 2	224	2
Batch 3	169	100
Micron	6000	< 44,000

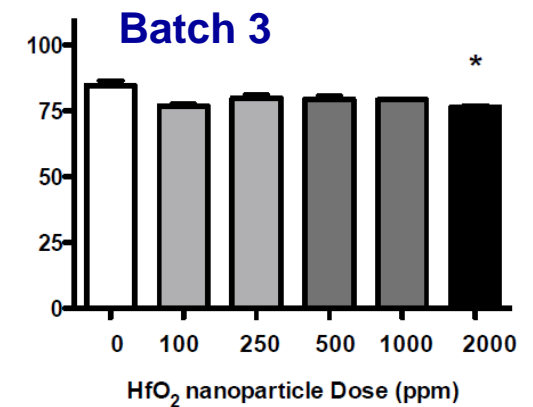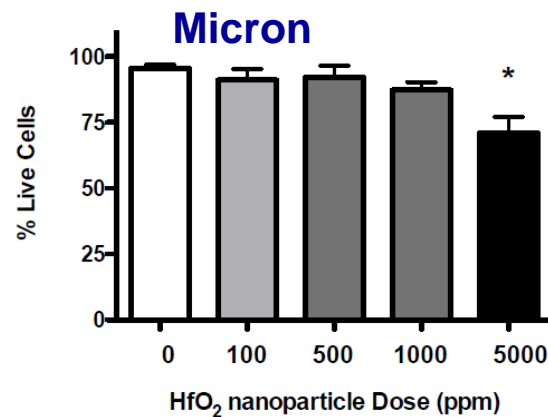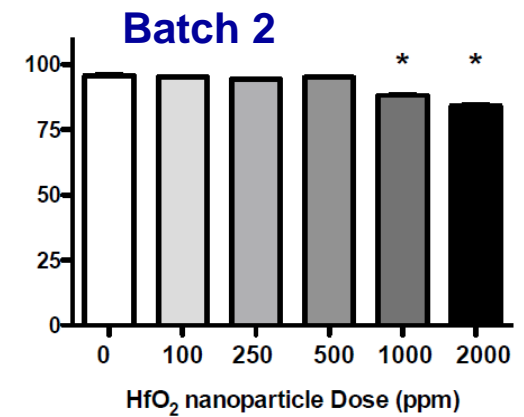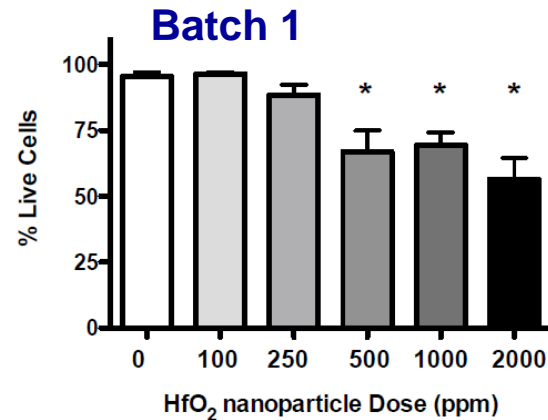

Results on CeO₂


Cerium oxide (MTI, "20 nm"). Example Microtox Test

Prep.	Measured avg size (nm)
Water	1741
+ Dispex	183

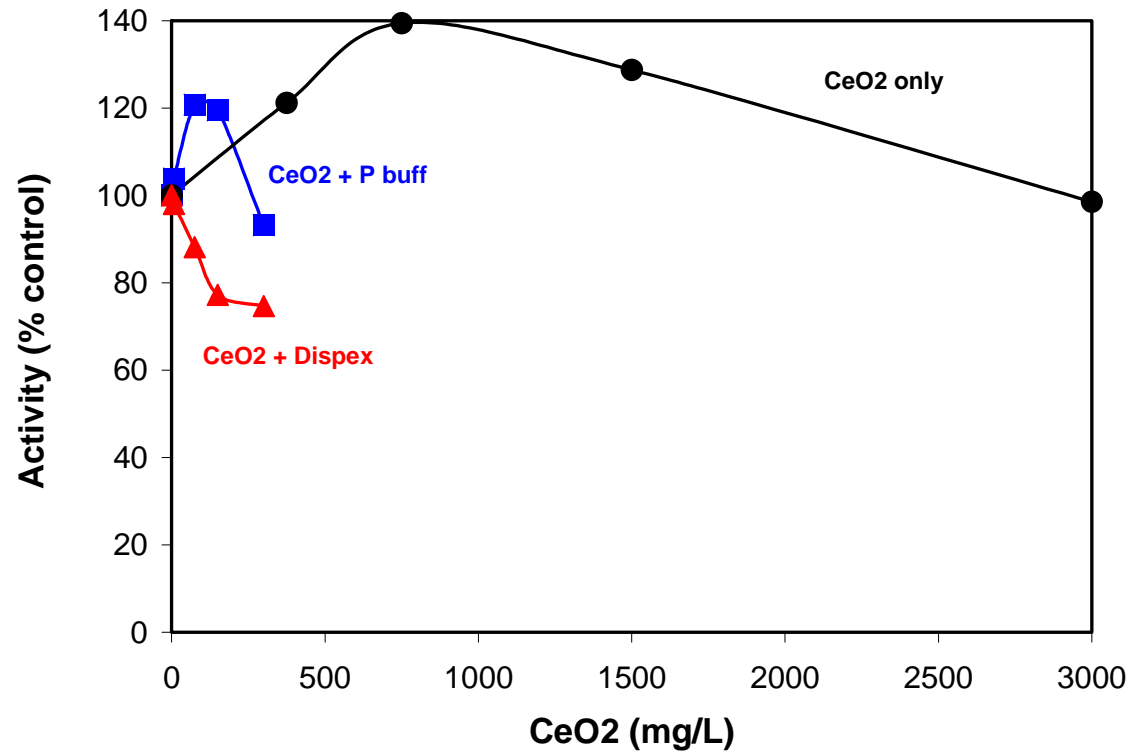


Results on CeO₂

Cerium oxide (MTI, “20 nm”). Example Live/Dead with Dispex

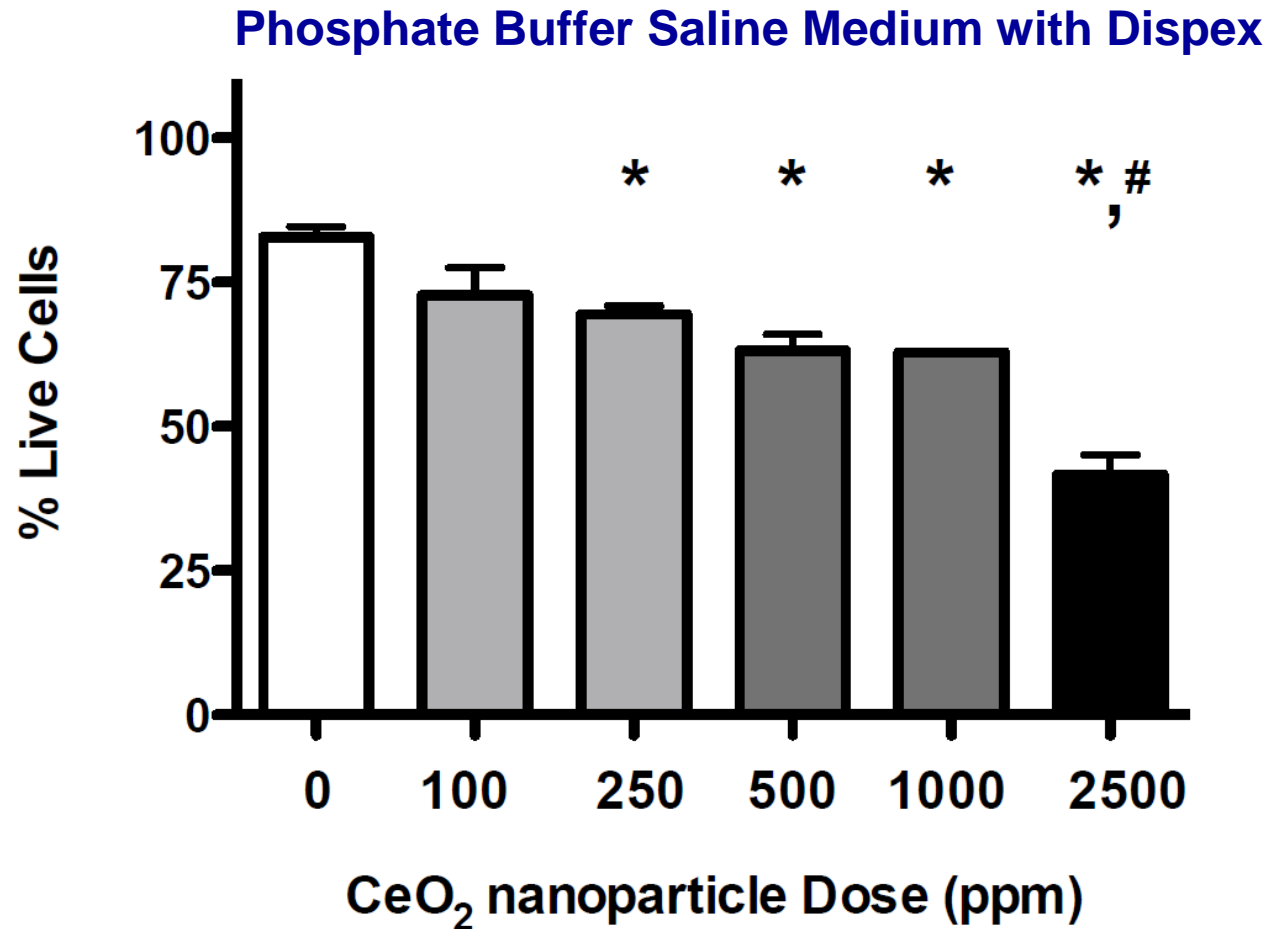


Results on Mn₂O₃

Manganese Oxide (SSNano, “40-60 nm”). Example Microtox with Dispex

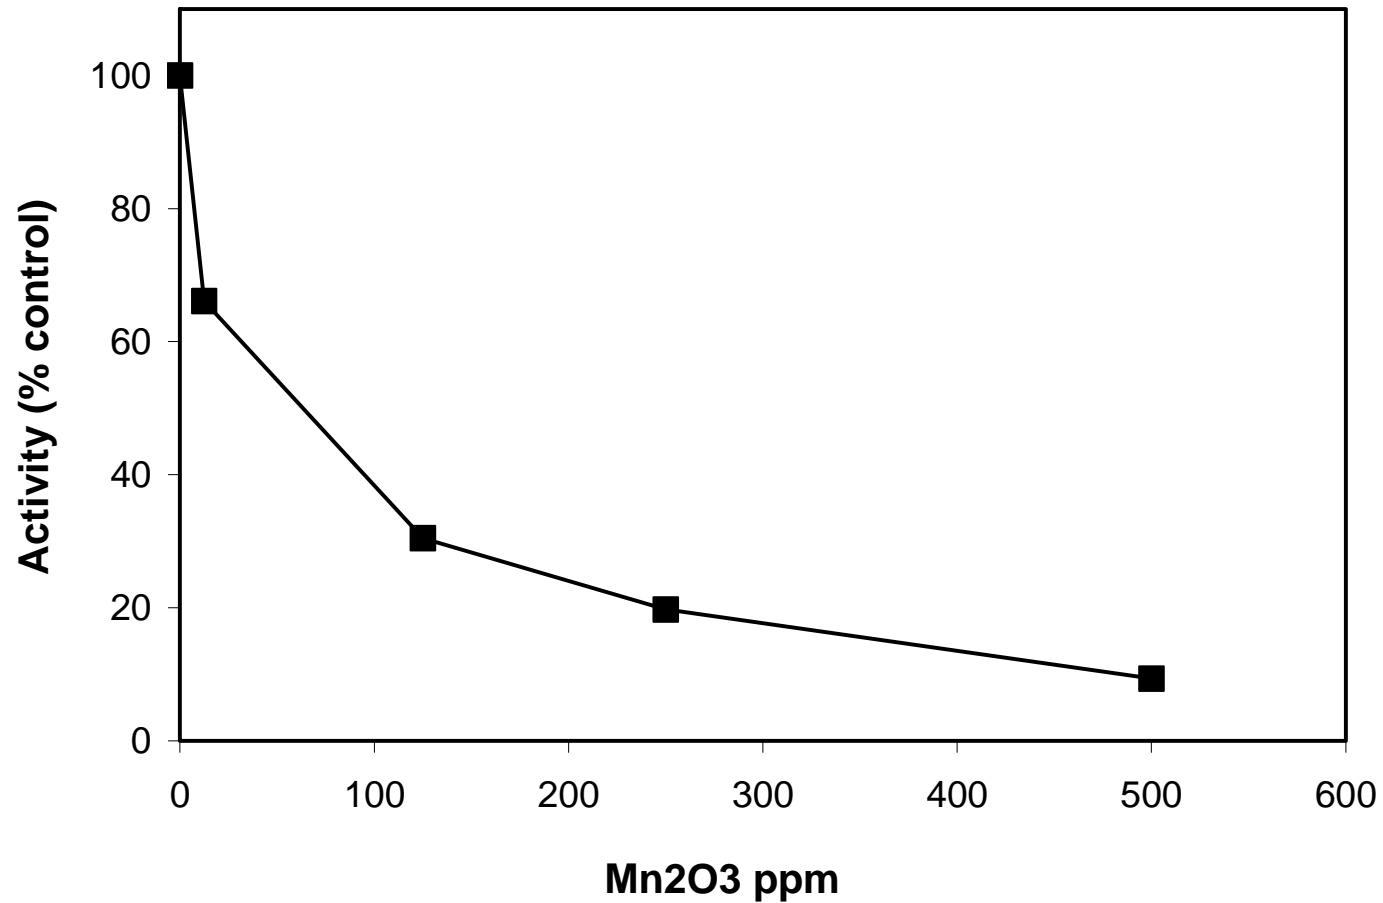


Hypothesis ROS

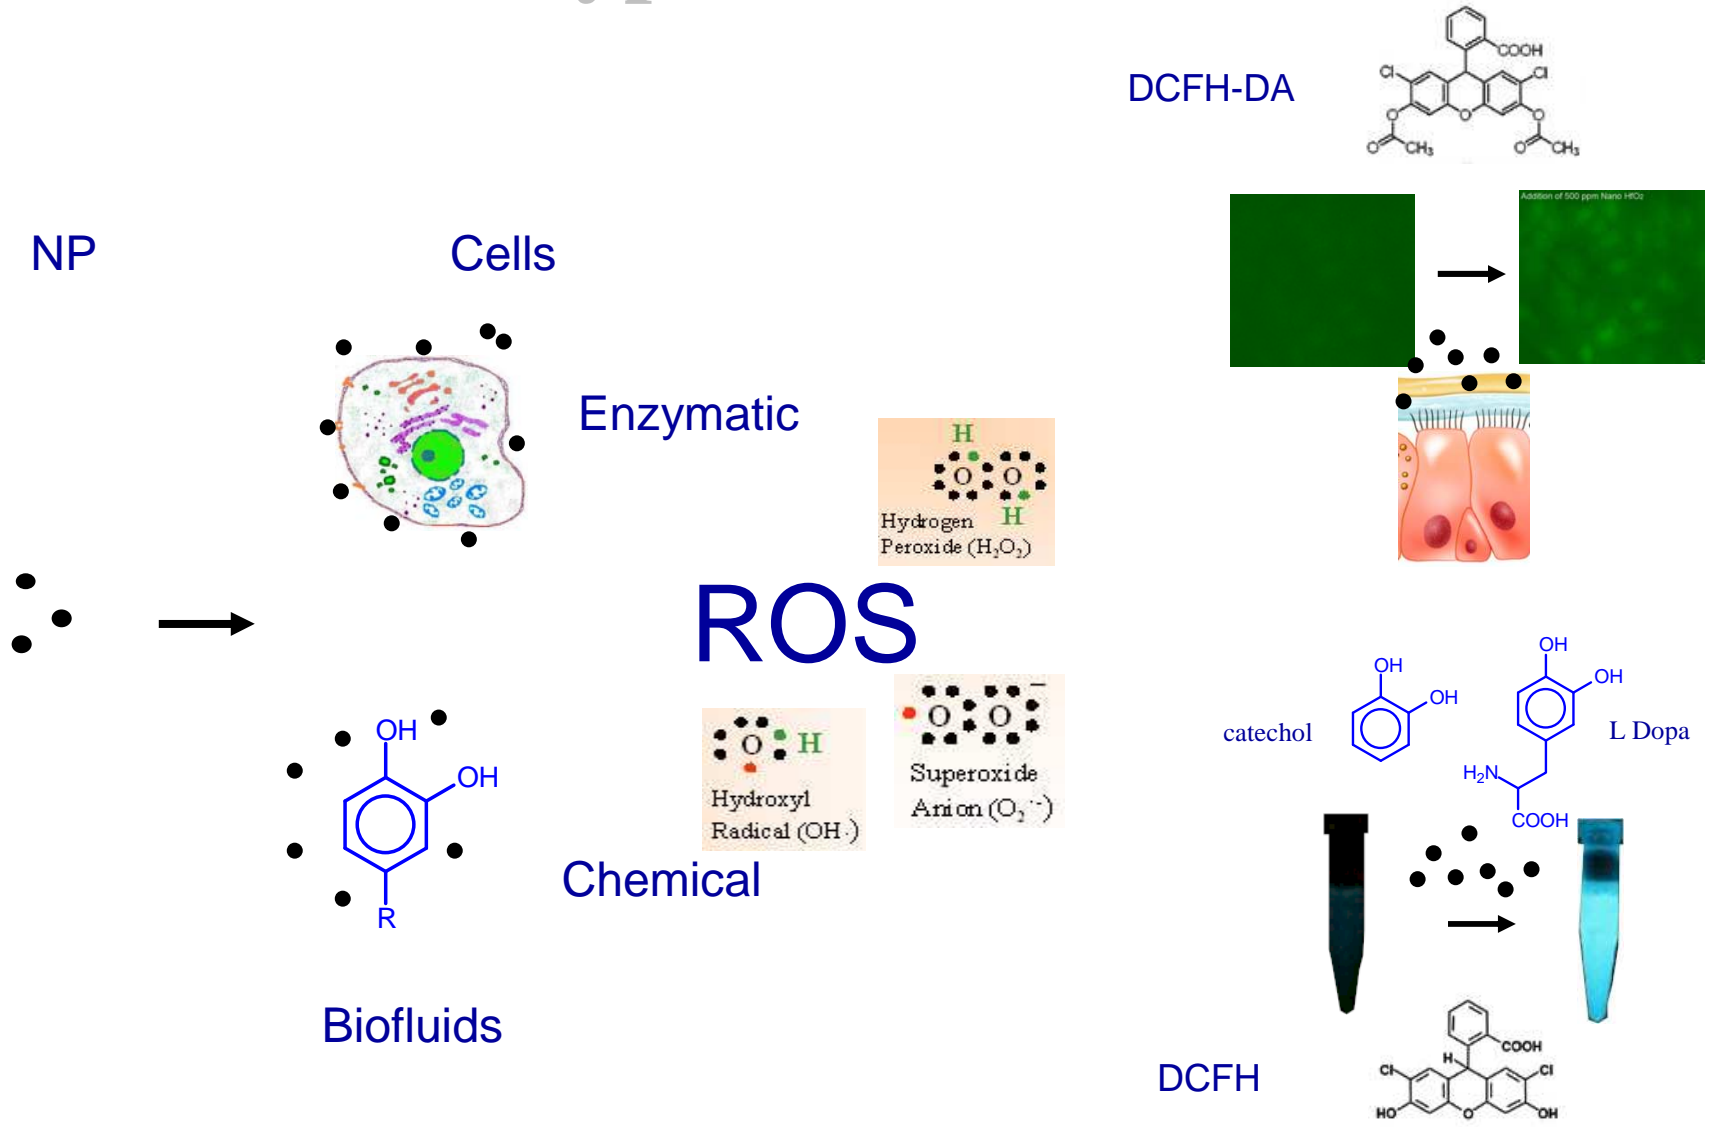

Chemical Production ROS


CeO₂ (MTI, “20 nm”)

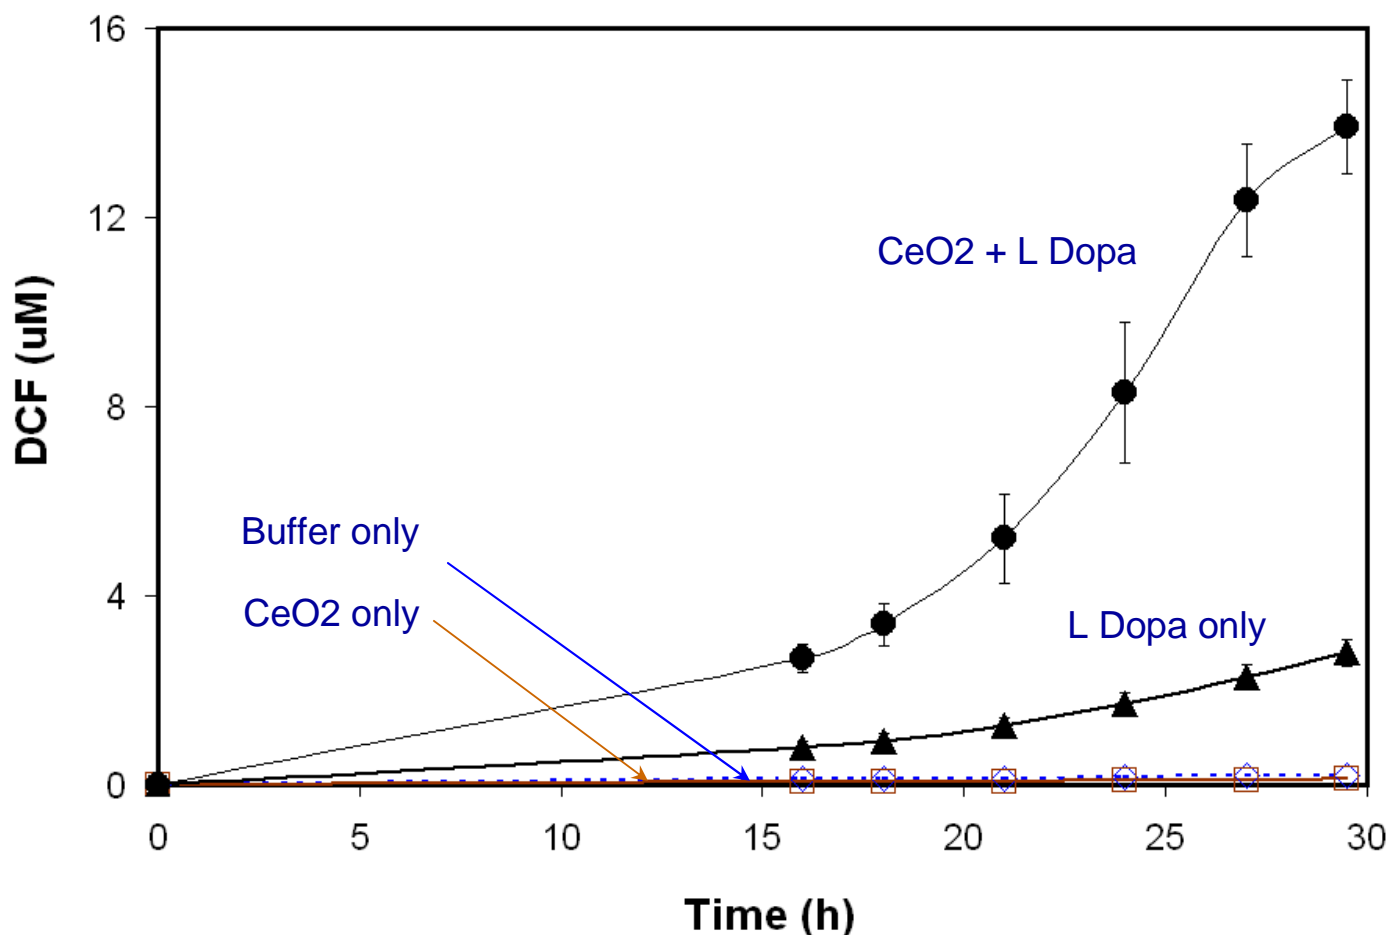

Results indicate that the oxidation of L Dopa by CeO₂ NP produces ROS. Direct reaction of CeO₂ with dissolved oxygen and water does not produce ROS


Chemical Production ROS

Mn₂O₃ SSNano “40-60 nm”).

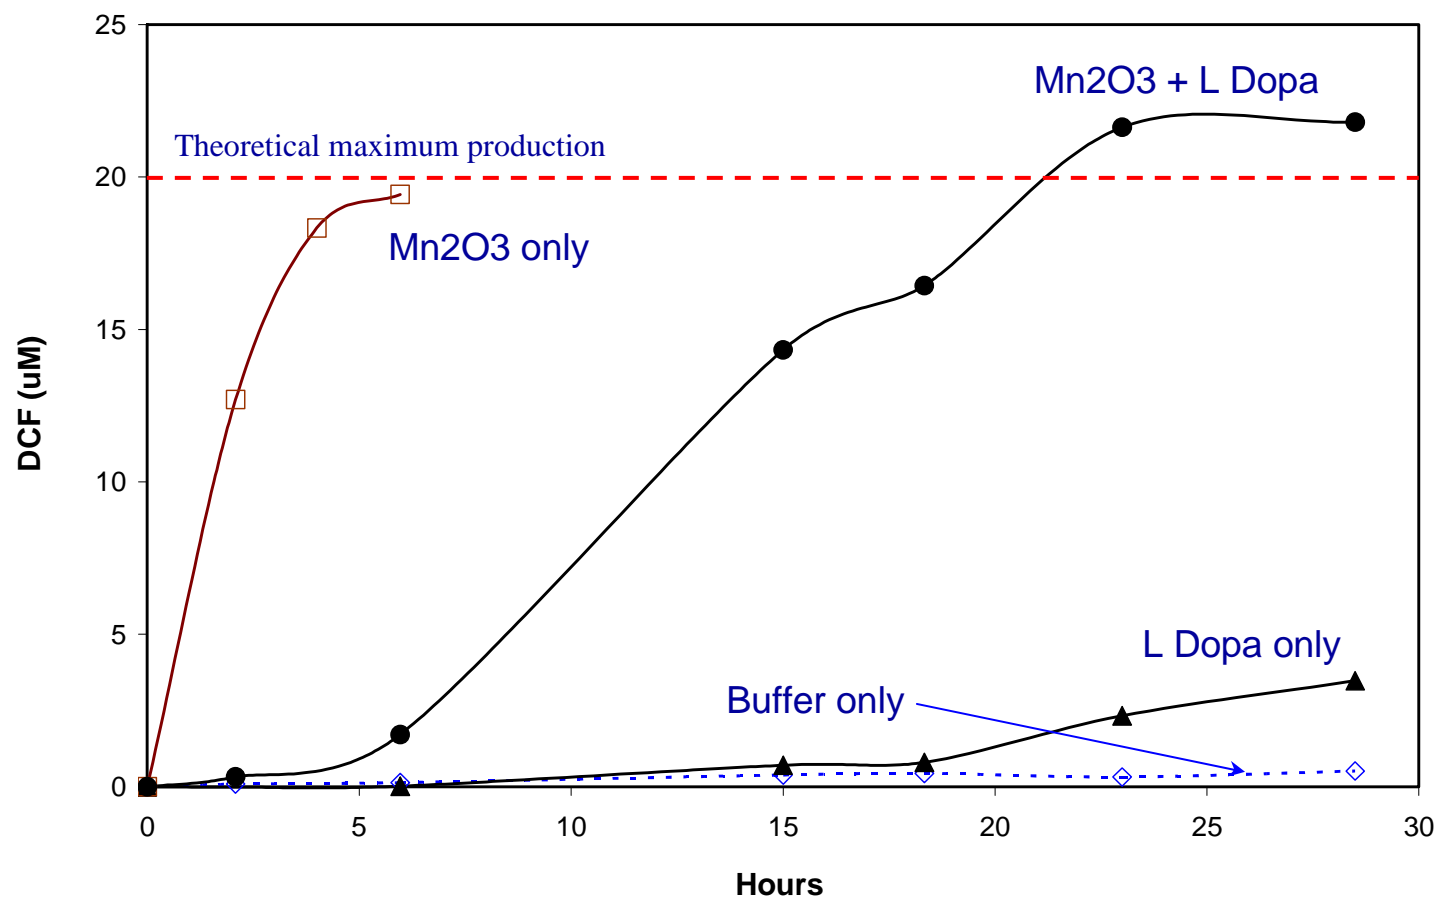

Results indicate that the interaction of Mn₂O₃ NP with water and dissolved oxygen causes the formation of ROS. L Dopa inhibits the formation of ROS by Mn₂O₃



Correspondence ROS Versus Inhibition

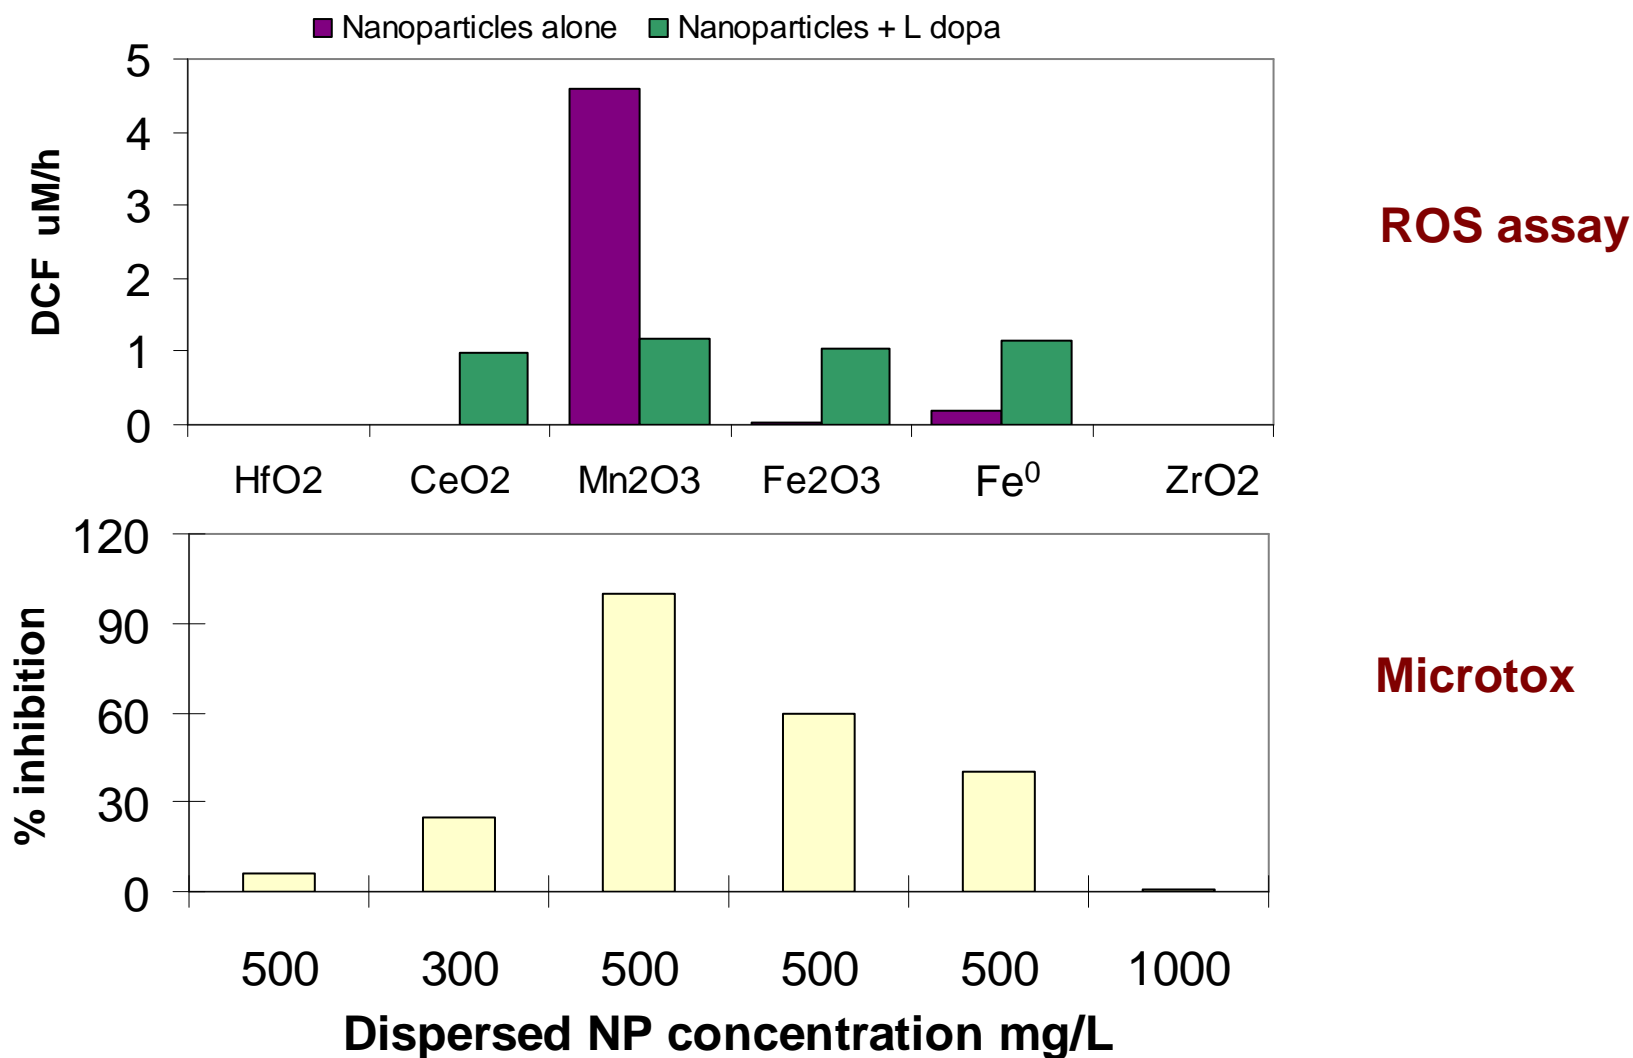


Development New Techniques

New dye-free techniques that are less prone to interferences

- xCELLigence based on measuring impedance

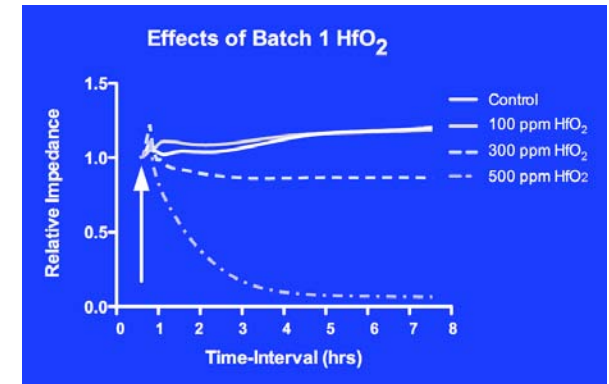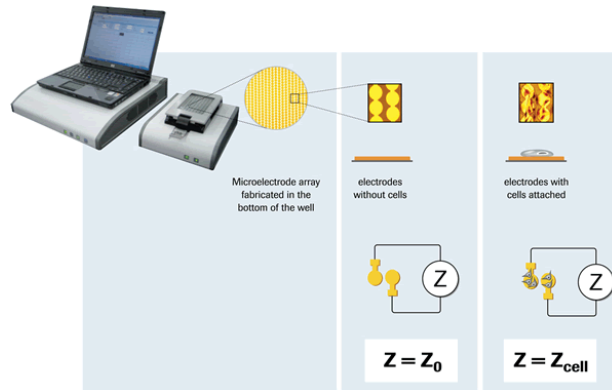

- Wound healing assay, based on time to close scrape wound


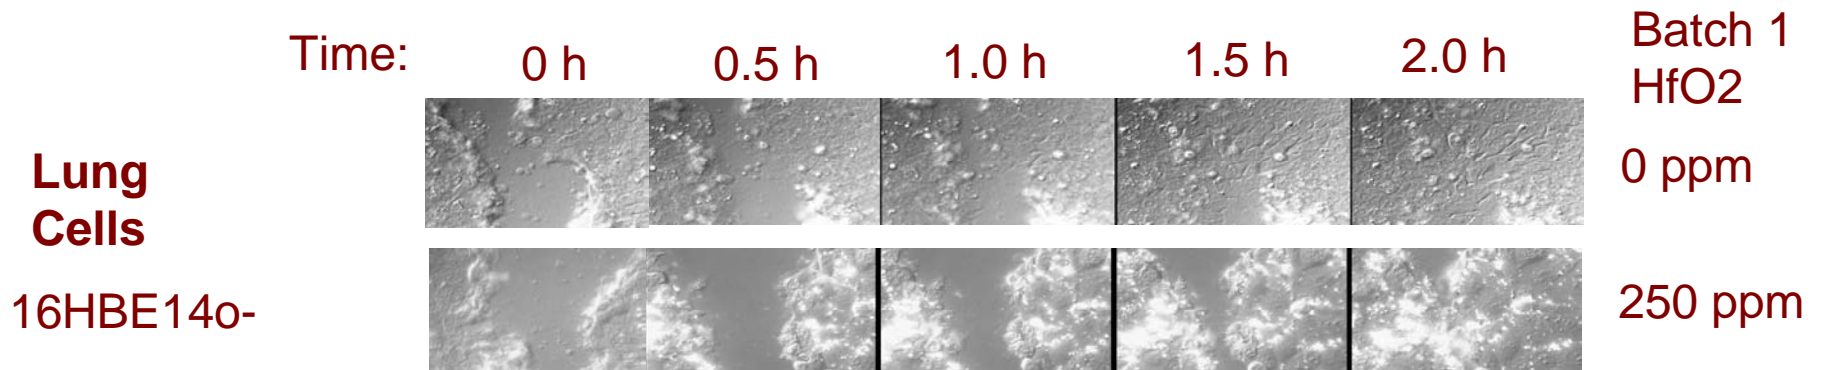


Development New Techniques

New dye-free techniques that are less prone to interferences (continued)

- O₂ uptake assay for yeast and bacterial cells

Inhibition of Yeast, *Saccharomyces cerevisiae*, by CeO₂

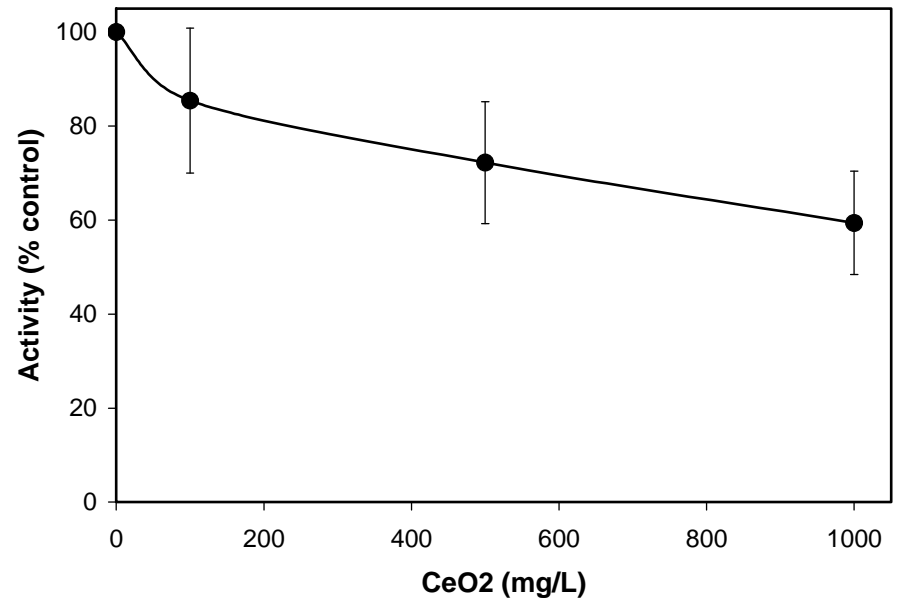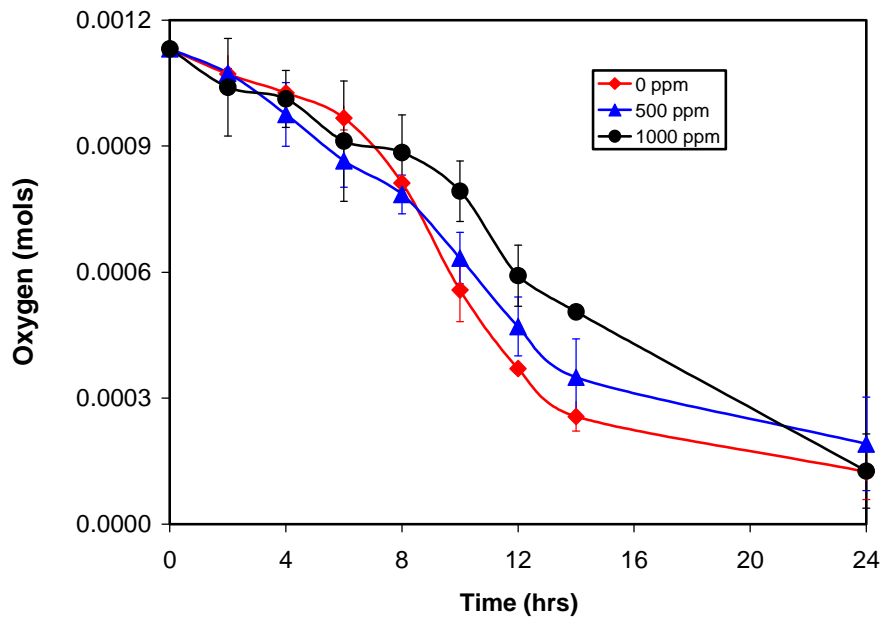

Preliminary Conclusions

- HfO₂, ZrO₂ and CeO₂ NPs mild to no toxicity.

Higher Toxicity of Batch 1 HfO₂ may be due to chemical contamination (from synthesis)

	L/D	Microtox	Methanog
	50% death	50% inhib	50% inhib
	----- mg/L -----		
HfO₂ *	>2000	3000	>2500
CeO₂	2500 **	>300 **	>1000
ZrO₂		>1000 **	

*batch3 **with dispersant

- NPs producing ROS directly in water most toxic. Chemical ROS production indicative of NP toxicity

Mn₂O₃ 50% IC microtox = 70 mg/L

Fe₂O₃ 50% IC microtox ≅ 500 mg/L

Fe⁰ 50% IC microtox ≅ 500 mg/L

Industrial Interactions and Technology Transfer

- **ISMI-Sematech (Steve Trammell, Laurie Beu)**
- **AMD (Reed Content)**
- **IBM (Arthur T. Fong)**
- **Intel (Steve W. Brown, Paul Zimmerman, Mansour Moinpour)**

Future Plans

Next Year Plans

- Fractionation of CeO₂ for toxicity study size fractions
- Biochemical indicators of oxidative stress
- Complete development of new non-dye based techniques

Long-Term Plans

- Rapid screening protocols of for assessing NP toxicity
- Toxicity to organ models

Publications, Presentations

- **Brownbag presentation: Nanoparticle Interaction with Biological Wastewater Treatment Processes, Water Sustainability Program, Phoenix, Arizona Jan 20th, 2010 at Arizona Cooperative Extension**
- **Sierra-Alvarez, R. 2009. Toxicity characterization of HfO₂ nanoparticles. SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing Teleseminar Series. August 6.**
- **Boitano, S. 2009. Measuring cytotoxicity of nanoparticles in human cells. SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing Teleseminar Series. Sept. 17.**
- **Ratner, B. 2009. Static SIMS: A Powerful Tool to Investigate Nanoparticles and Biology. SRC/Sematech Engineering Research Center for Environmentally Benign Semiconductor Manufacturing Teleseminar Series. May 14.**